
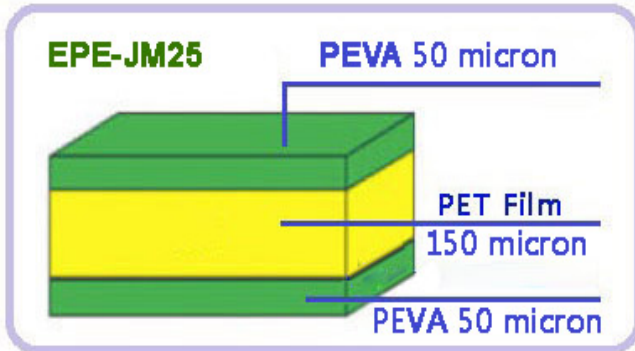


ITEM No./ 型号 : EPE-JM25

www.jingmaosolar.com

Stock Code/股票代码 : 838874

Isolation Sheet



		Unit 单位	Quoted Standard 测试标准	Standard Value	Result Value
Film Thickness 背板厚度	Nominal Thickness 标称厚度	μM	Micrometer GB/P 13542.2-2009	250±10	251
Tensile Strength (MD) 抗张强度		Mpa	ASTM D-882	≥100	109
Tensile Strength (TD) 抗张强度		Mpa	ASTM D-882	≥100	114
Elongation at Break (MD) 断裂伸长率		%	ASTM D-882	≥100	121
Elongation at Break (TD) 断裂伸长率		%	ASTM D-882	≥100	106
Shrinkage 150°C X 30min (MD)收缩率		%	GB/T 13541-92	≤1.5	1.1
Shrinkage 150°C X 30min (TD)收缩率		%	GB/T 13541-92	≤1.0	0.65
FLUORO/PET Peel Strength 层间剥离强度		N/10mm	GB/T2790-1995	~	~
Peeling Strength With EVA(initial) 与EVA粘接强度		N/cm	ASTMD903	≥40	85
Breakdown Voltage Strength 击穿电压强度		KV	ASTM D-149	≥18	20.5
Partial Discharge 局部放电		VDC	IEC 60664-1:2007	≥1000	1032
Water Vapor Transmission Rates 水汽透过率		g/m ² .d	GB/T 26253-2010	≤1.5	1.2
Damp-Heat Testing 耐湿热老化试验		85°CX85%RH 1000H	IEC 61215-2005	△b≤2,no bubble, delamination or fold	
UV Pretreatment 紫外预处理		UVA+UVB 30kwh/M ²	IEC 61215-2005	△b≤2,no bubble, delamination or fold	

Certified by



Cutting Sheet Accordingly

根据要求切条